

# UNCLASSIFIED

AD NUMBER	
AD153139	
CLASSIFICATION CHANGES	
TO:	unclassified
FROM:	confidential
LIMITATION CHANGES	
TO:	Approved for public release, distribution unlimited
FROM:	Distribution authorized to U.S. Gov't. agencies and their contractors; Administrative/Operational Use; JUL 1957. Other requests shall be referred to Army Ordnance Corps., Frankford Arsenal, PA.
AUTHORITY	
ARRADCOM ltr 19 Nov 1979; ARRADCOM ltr 19 Nov 1979	

THIS PAGE IS UNCLASSIFIED

**UNCLASSIFIED**

**AD 153 139**

**CLASSIFICATION CHANGED**

**TO: UNCLASSIFIED**

**FROM: CONFIDENTIAL**

**AUTHORITY:**

**ARRADCOM 1+r**

**19 NOV 79**



**UNCLASSIFIED**

**AD 153139**

**Armed Services Technical Information Agency**

**ARLINGTON HALL STATION  
ARLINGTON 12 VIRGINIA**

**FOR  
MICRO-CARD  
CONTROL ONLY**

**1 OF 1**

**NOTICE: WHEN GOVERNMENT OR OTHER DRAWINGS, SPECIFICATIONS OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY RELATED GOVERNMENT PROCUREMENT OPERATION, THE U. S. GOVERNMENT THEREBY INCURS NO RESPONSIBILITY, NOR ANY OBLIGATION WHATSOEVER; AND THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED, FURNISHED, OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA IS NOT TO BE REGARDED BY IMPLICATION OR OTHERWISE AS IN ANY MANNER LICENSING THE HOLDER OR ANY OTHER PERSON OR CORPORATION, OR CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERETO.**

CONFIDENTIAL

AD No. 153189

ASTIA FILE COPY

# FRANKFORD ARSENAL

MAP

REPORT NO. R-1395

Copy No. 32



FC

BALLISTIC TESTS OF  
2024-T4 AND 7075-T6 ALUMINUM ALLOYS (U)

By

*J. R. Kyrer*  
J. R. KYRER

*H. E. Fitzinger*  
H. E. FITZINGER

July 1957

OCO Project No. T4-005  
DA Project No. 5891-32-005

58 AA 343

PITMAN-DUNN LABORATORIES GROUP  
FRANKFORD ARSENAL  
Philadelphia, Pa.

FEB 13 1958

CONFIDENTIAL

REGRADING DATA CANNOT BE PREDETERMINED

This document is the property of the United States Government. It is furnished for the duration of the contract and shall be returned when no longer required, or upon recall by ASTIA to the following address:  
Armed Services Technical Information Agency, Arlington Hall Station,  
Arlington 12, Virginia

**NOTICE: THIS DOCUMENT CONTAINS INFORMATION AFFECTING THE NATIONAL DEFENSE OF THE UNITED STATES WITHIN THE MEANING OF THE ESPIONAGE LAWS, TITLE 18, U.S.C., SECTIONS 793 and 794. THE TRANSMISSION OR THE REVELATION OF ITS CONTENTS IN ANY MANNER TO AN UNAUTHORIZED PERSON IS PROHIBITED BY LAW.**

# CONFIDENTIAL

Initial distribution of this report has been made in accordance with the distribution list contained herein.

Ordnance Corps installations will make requests for copies direct to Armed Services Technical Information Agency (ASTIA), Document Service Center, Knott Building, Dayton 2, Ohio.

Department of Defense agencies other than Ordnance Corps, as well as Government agencies outside the Department of Defense, and Ordnance Corps and other Department of Defense agency contractors having approved Field of Interest Registers on file with ASTIA will make requests for copies to ASTIA through the Commanding Officer, Diamond Ordnance Fuze Laboratories, Washington 25, D. C., Attn: Technical Reference Section.

If no approved Field of Interest Register is on file with ASTIA, Department of Defense agency contractors will transmit requests for copies through the appropriate screening point for certification of "need-to-know," to the Commanding Officer, Diamond Ordnance Fuze Laboratories, Attn: Technical Reference Section.

# CONFIDENTIAL

**CONFIDENTIAL**

REPORT No. R-1395

Copy No.

**BALLISTIC TESTS OF  
2024-T4 AND 7075-T6 ALUMINUM ALLOYS (U)**

July 1957

OCO Project No. TB4-005  
DA Project No. 5B93-32-005

Prepared by

*J. R. Kymer*  
J. R. KYMER  
Physicist

*H. E. Patzinger*  
H. E. PATZINGER  
Physicist

Reviewed by

G. C. WHITE, JR.,  
Chief  
Physics and Mathematics Branch

W. J. KROEGER  
Director  
Physics Research Laboratory

Approved by

*C. C. Fawcett*  
C. C. FAWCETT  
Director  
Pitman-Dunn Laboratories Group

For

JAMES A. RICHARDSON, III  
Brigadier General, USA  
Commanding

FRANKFORD ARSENAL  
Pitman-Dunn Laboratories Group  
Philadelphia 37, Pa.

**CONFIDENTIAL**

REGRADING DATA CANNOT BE PREDETERMINED

58 AA · 343

# CONFIDENTIAL

## TABLE OF CONTENTS

	<u>Page</u>
INTRODUCTION	1
MATERIALS AND METHODS	1
Plate	1
Projectiles	2
RESULTS AND DISCUSSION	2
2024-T4 and 7075-T6 Alloys vs 20 mm AP M95 Projectiles	4
2024-T4 and 7075-T6 Alloys vs 20 mm AP T33 Projectiles	5
2024-T4 and 7075-T6 Alloys vs Caliber .50 AP M2 Projectiles	5
20 mm AP M95 and 20 mm AP T33 Projectiles vs 2024-T4 Alloy	5
20 mm AP M95 and 20 mm AP T33 Projectiles vs 7075-T6 Alloy	6
Spalling	6
CONCLUSIONS	7
REFERENCES	8
FIGURES	9
Distribution	20

CONFIDENTIAL



# CONFIDENTIAL

## OBJECT

To systematically evaluate the ballistic resistance of 2024-T4 and 7075-T6 aluminum alloy plates when subjected to small arms projectile firings.

## SUMMARY

Aluminum alloys 2024-T4 and 7075-T6, in 1/8, 1/4, 1/2, 3/4, 1, and 1 1/2 inch thicknesses were tested for ballistic resistance to penetration and spalling at plate obliquities of 0, 30, 45, 55, 60, 65, 70, and 80 degrees. Caliber .50 AP M2, 20 mm AP M95, and 20 mm AP T33 projectiles were used in this investigation.

For armor purposes, the 2024-T4 alloy is generally superior to the 7075-T6 alloy with respect to ballistic protection, and spalls considerably less. For defeating aluminum alloys of these types, the 20 mm AP T33 projectile is generally superior to the 20 mm AP M95 projectile.

## AUTHORIZATION

Sub RAD ORDTB 2-1064, 22 December 1953.

CONFIDENTIAL

# CONFIDENTIAL

## INTRODUCTION

In the future it is quite likely that aluminum alloys will be used instead of steel for armor purposes on various types of lightly armored military vehicles. It is known that some aluminum alloys exposed at intermediate and high obliquities provide better ballistic protection against exploded shell fragments and small caliber projectile firings than steel armor of equivalent weight.

Results of this work are reviewed in Reference 1.\* Ballistic and mechanical tests conducted at this arsenal<sup>(2)</sup> and at Case Institute of Technology,<sup>(3,4)</sup> respectively, have shown that resistance to penetration for 1/2 inch thick plate is linearly proportional to hardness, regardless of alloy composition, toughness, ductility, or any other mechanical property evaluated, up to approximately 120 Bhn. In hardness ranges exceeding 120 Bhn, the ballistic limit-hardness relation was no longer only linear, but became dependent upon toughness also.

Substitution of aluminum alloys which afford the same ballistic protection as steel would also provide a considerable weight saving. This is a very important factor in air-borne vehicle considerations.

The frontal armor of most military vehicles is exposed at obliquities of attack greater than 45 degrees. Military aircraft is constructed mainly of aluminum alloys and, in combat, is also exposed at very high obliquity conditions of impact. In the past other military installations have investigated the ballistic resistance of different aluminum alloys for various target conditions which did not include very high obliquities. This program, therefore, was planned and conducted to systematically investigate the majority of potential targets (armored and aircraft) which might be subjected to small caliber projectile firings. It included thicknesses varying from 1/8 to 1 1/2 inches, and obliquities ranging from 0 to 80 degrees.

## MATERIALS AND METHODS

### Plate

Commercial alloys 2024-T4 and 7075-T6, in thicknesses of 1/8, 1/4, 1/2, 3/4, 1, and 1 1/2 inches, were used in this investigation. These alloys were chosen because they were considered to offer more resistance

---

\*See attached REFERENCES

# CONFIDENTIAL

# CONFIDENTIAL

to projectile penetration than some of the other commercially available ones. Furthermore, some ballistic data already existed for these alloys. (Some of the ballistic and mechanical properties of alloys 2024-T4 and 7075-T6 are discussed in Reference 1.)

Ob.

## Projectiles

Caliber .50 AP M2, 20 mm AP M95, and 20 mm AP T33 projectiles were used in these tests. The first two types are standard rounds; the third type is a scale model of the 90 mm AP T33 shot. The latter round was chosen since extensive tests against steel armor have been made at the 20 mm scale at this arsenal and, at Watertown Arsenal, at the caliber .40 scale.

## RESULTS AND DISCUSSION

The test conditions and a summary of the ballistic results are presented in Table I. The data are presented graphically in Figures 1 through 5. In order to compare alloy resistance to penetration of projectiles of two different weights and diameters, the specific limit energy,\* rather than the ballistic limit, was used in these performance graphs. In Figures 1, 2, and 3 the protection ballistic limit (PBL)\*\* is also indicated at the right side of the graph. Since data for projectiles of different weights are plotted in Figures 4 and 5, no scale for the PBL is given.

\*The specific limit energy is the kinetic energy of the projectile divided by the cube of its diameter, or

$$\frac{WV_L^2}{d^3}$$

where

W = weight of the projectile in pounds

V<sub>L</sub> = limit velocity of the plate in feet per second

d = diameter of the projectile in inches.

\*\*A protection-complete penetration is obtained whenever a fragment or fragments of either the impacting projectile or the plate are ejected from the rear of the plate with sufficient energy to perforate a thin, mild steel plate (about 0.020 in.) or equivalent screen placed parallel to and approximately six inches rearward of the plate.

# CONFIDENTIAL

Table I. Summary of Ballistic Results for  
2024-T4 and 7075-T6 Aluminum Alloys

Obliquity (°)	Projectile	Alloy	Protection Ballistic Limits (fps)					
			1/8 in.	1/4 in.	1/2 in.	3/4 in.	1 in.	1 1/2 in.
0	T33	2024-T4	-	-	-	-	1123	1670
		7075-T6	-	-	-	-	1030	1420
	M95	2024-T4	-	-	-	-	1310	1680
		7075-T6	-	-	-	-	970	1510
	M2	2024-T4	-	-	-	1365	1670	2030
		7075-T6	-	-	-	1260	1695	2075
30	T33	2024-T4	-	-	-	-	1390	1905
		7075-T6	-	-	-	-	1285	1875
	M95	2024-T4	-	-	-	-	1455	1920
		7075-T6	-	-	-	-	1415	1965
	M2	2024-T4	-	-	-	1350	1660	2225
		7075-T6	-	-	-	1420	1820	2385
45	T33	2024-T4	-	-	-	1500	1860	2360
		7075-T6	-	-	-	1390	1795	2460
	M95	2024-T4	-	-	-	1510	1950	2475
		7075-T6	-	-	-	1410	1935	2535
	M2	2024-T4	-	-	1505	1735	2285	3080
		7075-T6	-	-	1535	2160	2530	3200
55	T33	2024-T4	-	-	-	-	-	2990
		7075-T6	-	-	-	-	-	3040
	M95	2024-T4	-	-	-	-	-	3010
		7075-T6	-	-	-	-	-	3255
	M2	2024-T4	-	-	1815	2460	3005	4050
		7075-T6	-	-	2030	2680	3400	>4190

# CONFIDENTIAL

Table I. Summary of Ballistic Results for  
2024-T4 and 7075-T6 Aluminum Alloys (Cont'd)

Obliquity (°)	Projectile	Alloy	Protection Ballistic Limits (fps)					
			1/8 in.	1/4 in.	1/2 in.	3/4 in.	1 in.	1 1/2 in.
60	T33	2024-T4	-	-	1450	1960	2730	3555
		7075-T6	-	-	1125	1760	2400	3510
	M95	2024-T4	-	-	1550	1845	2140	3465
		7075-T6	-	-	1230	1720	2325	3400
	M2	2024-T4	1000	1475	2230	2945	3620	-
		7075-T6	895	1330	2220	2900	3750	-
	T33	2024-T4	-	-	1660	2260	3090	-
		7075-T6	-	-	1120	1930	2720	-
65	M95	2024-T4	-	-	1705	1945	2600	-
		7075-T6	-	-	1380	1885	2580	-
	T33	2024-T4	-	-	1905	2745	3580	-
		7075-T6	-	-	1375	2220	3015	-
	M95	2024-T4	-	-	1955	2200	2840	-
		7075-T6	-	-	1455	2405	3175	-
	M2	2024-T4	1130	1825	3150	-	-	-
		7075-T6	1090	1715	2870	-	-	-
70	M2	2024-T4	1575	2710	>4200	-	-	-
		7075-T6	1430	2650	>4450	-	-	-
80	M2	2024-T4	1575	2710	>4200	-	-	-
		7075-T6	1430	2650	>4450	-	-	-

2024-T4 and 7075-T6 Alloys  
vs  
20 mm AP M95 Projectiles

Figure 1 shows the behavior of the AP M95 projectiles as a function of obliquity for various plate thicknesses. For the majority of conditions, the 2024-T4 plate is somewhat superior to the 7075-T6 plate in defeating the M95 shot. Against thin plate, i. e., 1/2 inch, this superiority is as much as 500 fps, or 62 per cent, on an energy basis. The exceptions are mostly for thick plate at high obliquity, such as 1-inch plate at 60° and 70° obliquities.

4  
CONFIDENTIAL

# CONFIDENTIAL

## 2024-T4 and 7075-T6 Alloys vs 20 mm AP T33 Projectiles

As shown in Figure 2, the 2024-T4 plate is superior to the 7075-T6 plate for stopping the T33 shot under all conditions of attack investigated, except for 1 1/2-inch plate at 45° and 55° obliquities. Under these conditions the two plates are approximately equivalent. The superiority of the 2024-T4 alloy is greater for the thin plates. Against the 1/2-inch plate at 65° obliquity, 120 per cent more energy and an additional 540 fps are required to defeat the 2024-T4 plate than the 7075-T6 plate. For the undermatching\* targets, the 7075-T6 plate spalls considerably, and complete penetrations often occur without the projectile perforating the plate. This is discussed more completely in the section entitled "Spalling."

## 2024-T4 and 7075-T6 Alloys vs Caliber .50 AP M2 Projectiles

Against the caliber .50 AP M2 projectiles (Figure 3), the 2024-T4 alloy is superior if the plate is undermatching; the 7075-T6 alloy is superior if the plate is overmatching.\*\* For matching\*\*\* targets the 7075-T6 plate is superior at obliquities less than 60°; the 2024-T4 is superior for obliquities greater than 60°.

## 20 mm AP M95 and 20 mm AP T33 Projectiles vs 2024-T4 Alloy

For the majority of target conditions investigated, the T33 projectile is more effective than the M95 projectile in defeating 2024-T4 plate (Figure 4). However, for intermediate plate thicknesses at high obliquity, the M95 is considerably superior (50 per cent on an energy basis for 1-inch plate at 60° obliquity).

\*Undermatching plate - thickness is less than projectile diameter.

\*\*Overmatching plate - thickness is greater than projectile diameter.

\*\*\*Matching plate - thickness is equal to projectile diameter.

# CONFIDENTIAL

## 20 mm AP M95 and 20 mm AP T33 Projectiles vs 7075-T6 Alloy

Under all conditions of attack the AP T33 projectile is equal or superior to the 20 mm AP M95 projectile in defeating 7075-T6 alloy (Figure 5). Against one target of 1-inch plate at 65° obliquity, the M95 projectile required about one per cent less limit energy than the T33, but this is not significant. The M95 projectile requires as much as 65 per cent more limit energy to defeat 1/2-inch plate at 65° obliquity than is needed by the T33 projectile.

### Spalling

Figures 6 to 11, incl, are photographs of the front and back surfaces of 1/2 and 1 1/2 inch thick 2024-T4 and 7075-T6 aluminum alloy plates after being subjected to 20 mm projectile firing. In Figure 6 (A and B), rounds 1 to 4 are 20 mm AP T33 projectile impacts and rounds 5 to 11 are 20 mm AP M95 projectile impacts, all at 60° obliquity. In Figure 7 (A and B), rounds 1 to 6 are 20 mm AP T33 projectile impacts and rounds 7 to 12 are 20 mm AP M95 projectile impacts. It may be noted that the projectile impacts on the front surfaces of the 2024-T4 and 7075-T6 plates are similar in appearance. However, the rear surfaces show considerable spalling for the 7075-T6 alloy, while the 2024-T4 plate shows practically no spalling. Figure 7B shows spalling for rounds 3, 5, 8, and 9, even though the projectiles only partially penetrated the plate.

Figures 8B and 9B show that 7075-T6 alloy spalls considerably more on the rear than 2024-T4 alloy for 1 1/2 inch thicknesses. Rounds 1 to 5 on Figure 8 (A and B) and rounds 1 to 7 on Figure 9 (A and B) represent 20 mm AP T33 projectile impacts at 60° obliquity.

Figures 10 (A and B) and 11 (A and B) show caliber .50 AP M2 projectile impacts on 1/4 inch thick 2024-T4 and 7075-T6 alloy plates set at 80° obliquity. It may be noted in Figure 10B that very little material is ejected from the rear of the 2024-T4 plate even though rather large projectile holes were produced without going through (note rounds 2 and 4 of Figure 10B). In contrast, the 7075-T6 plate, which had a similar ballistic limit, 2650 fps (Table I), spalled considerably more (Figure 11B).

# CONFIDENTIAL

## CONCLUSIONS

1. The 2024-T4 aluminum alloy is generally superior to the 7075-T6 alloy with respect to ballistic protection, and spalls considerably less.

2. On the whole, the 20 mm AP T33 projectile is superior to the 20 mm AP M95 projectile for defeating aluminum alloy plates of these two types.



# CONFIDENTIAL

## REFERENCES

1. H. P. George, "Light Alloy Armor Plate (Review of Work to March 1950)," Frankford Arsenal Report R-974, June 1950 (Confidential)
2. H. E. Fatzinger, "Caliber .30 Penetration Tests of Various Experimentally Fabricated Aluminum Alloy Plates," Frankford Arsenal Report R-926, July 1949.
3. W. M. Baldwin, Jr., L. J. Ebert, M. L. Fried, and R. P. Frohberg, "The Properties of Heavy Gage Aluminum Alloys for Armor," Case Institute of Technology Final Report on Contract W33-019-ORD-6061, March 1950.
4. W. M. Baldwin, Jr., L. J. Ebert, E. P. Weber, C. A. Beiser, and D. J. Garibotti, "Investigation of Light Alloy Armor," Case Institute of Technology Final Report on Contract DA 33-019-ORD-811, June 1953.

CONFIDENTIAL

CONFIDENTIAL


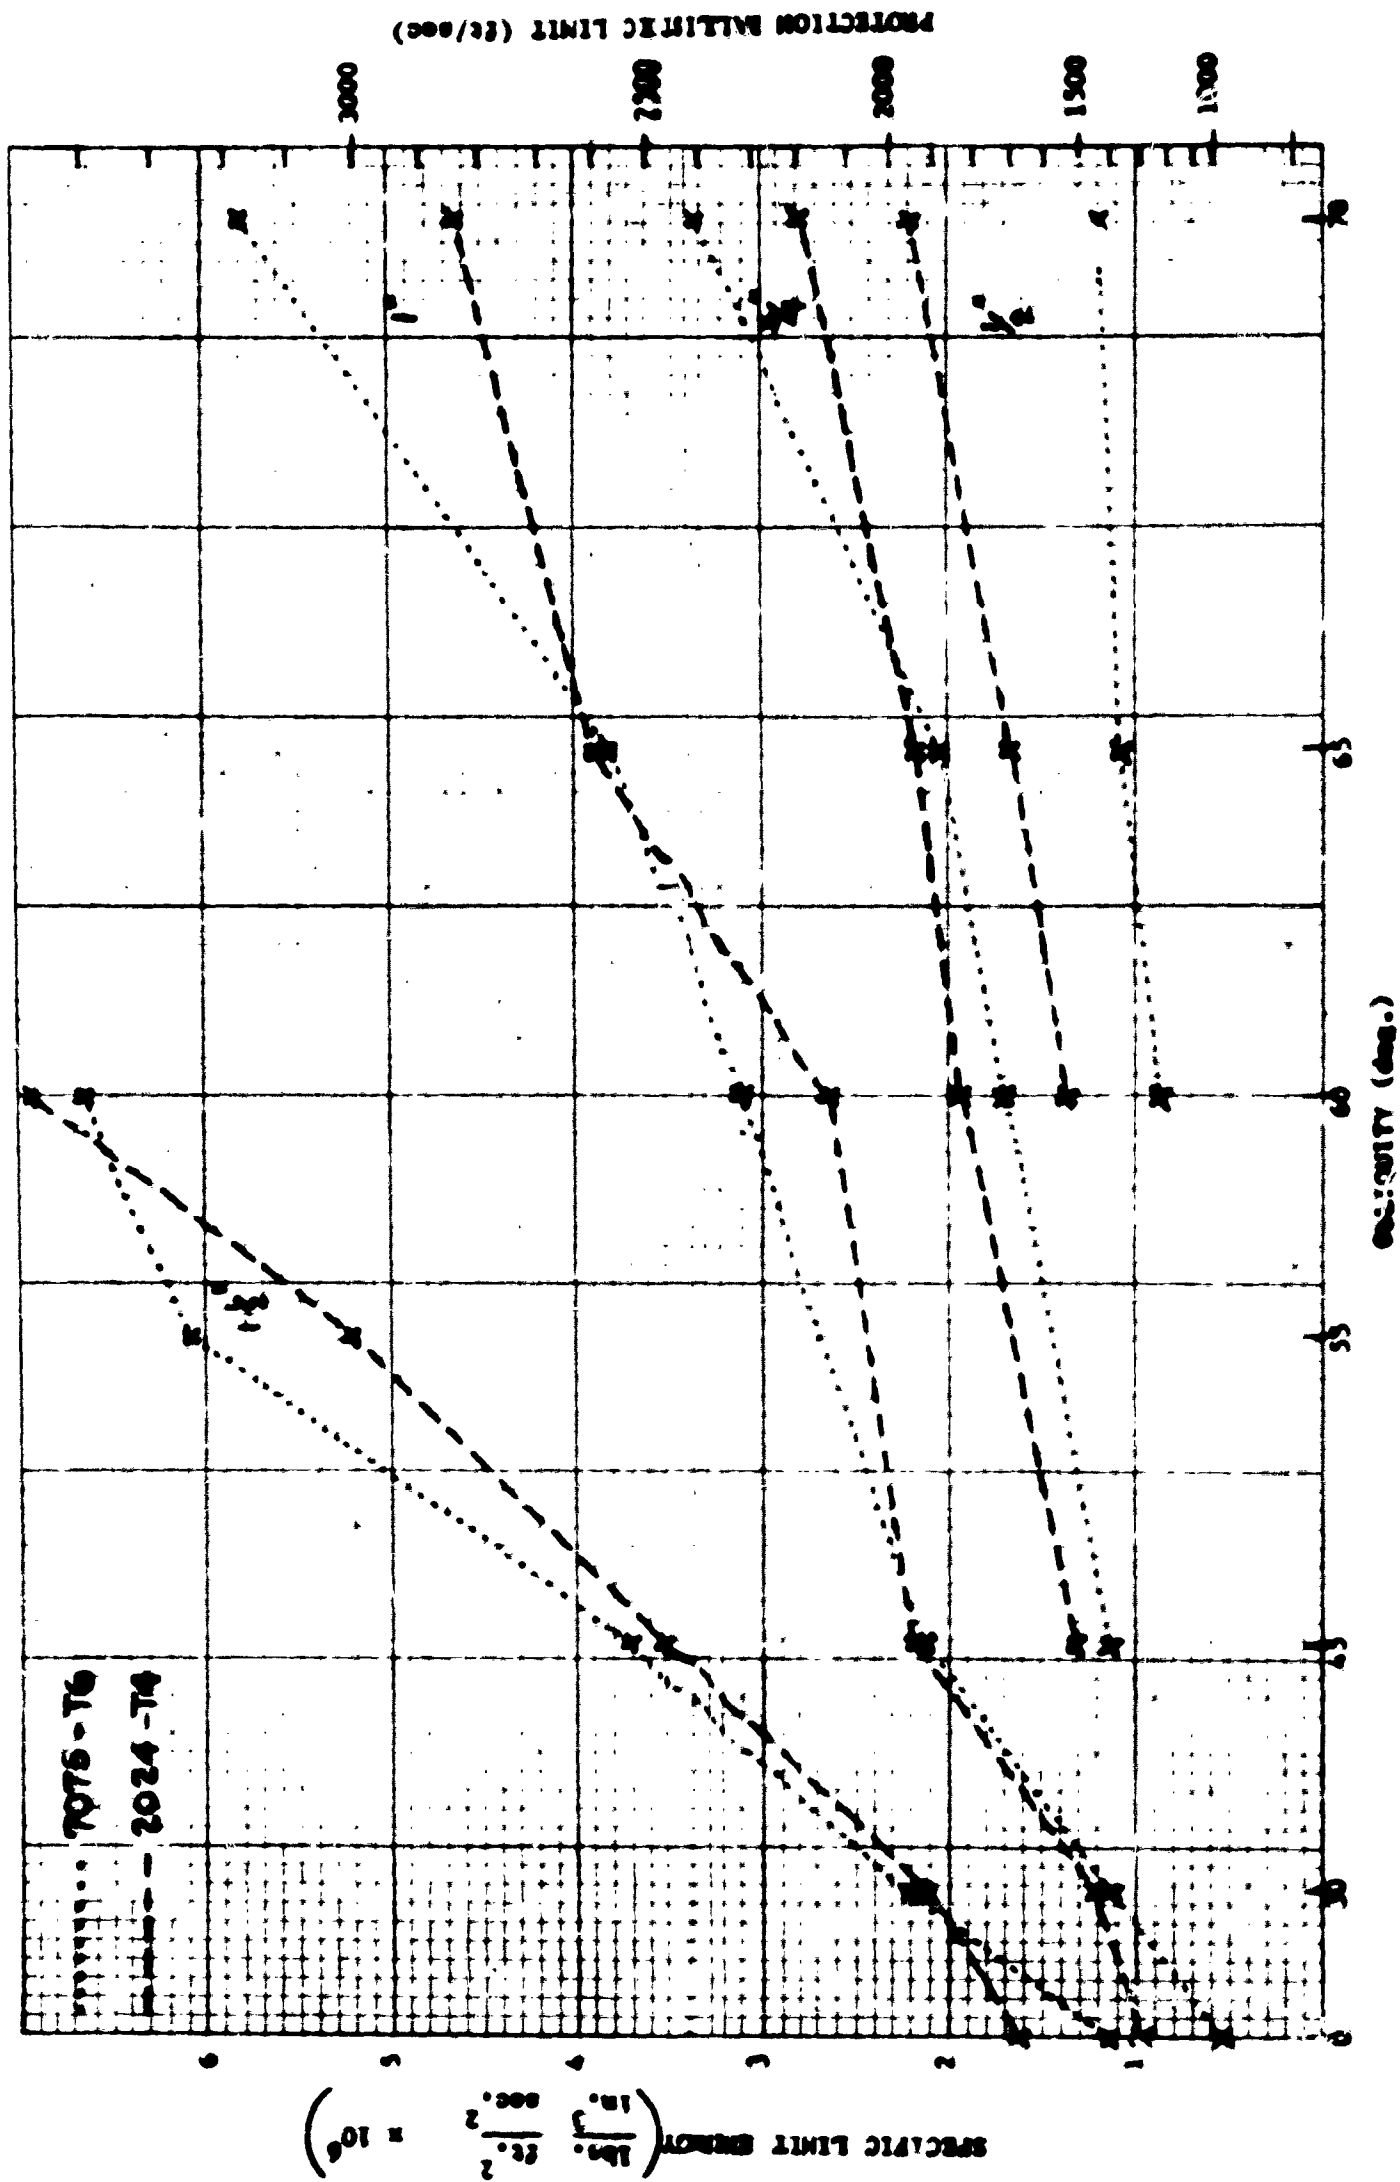


Figure 1. Ballistic resistance of 2024-T4 and 7075-T6 aluminum alloy plate vs 20 mm AP M95 projectiles

CONFIDENTIAL


CONFIDENTIAL

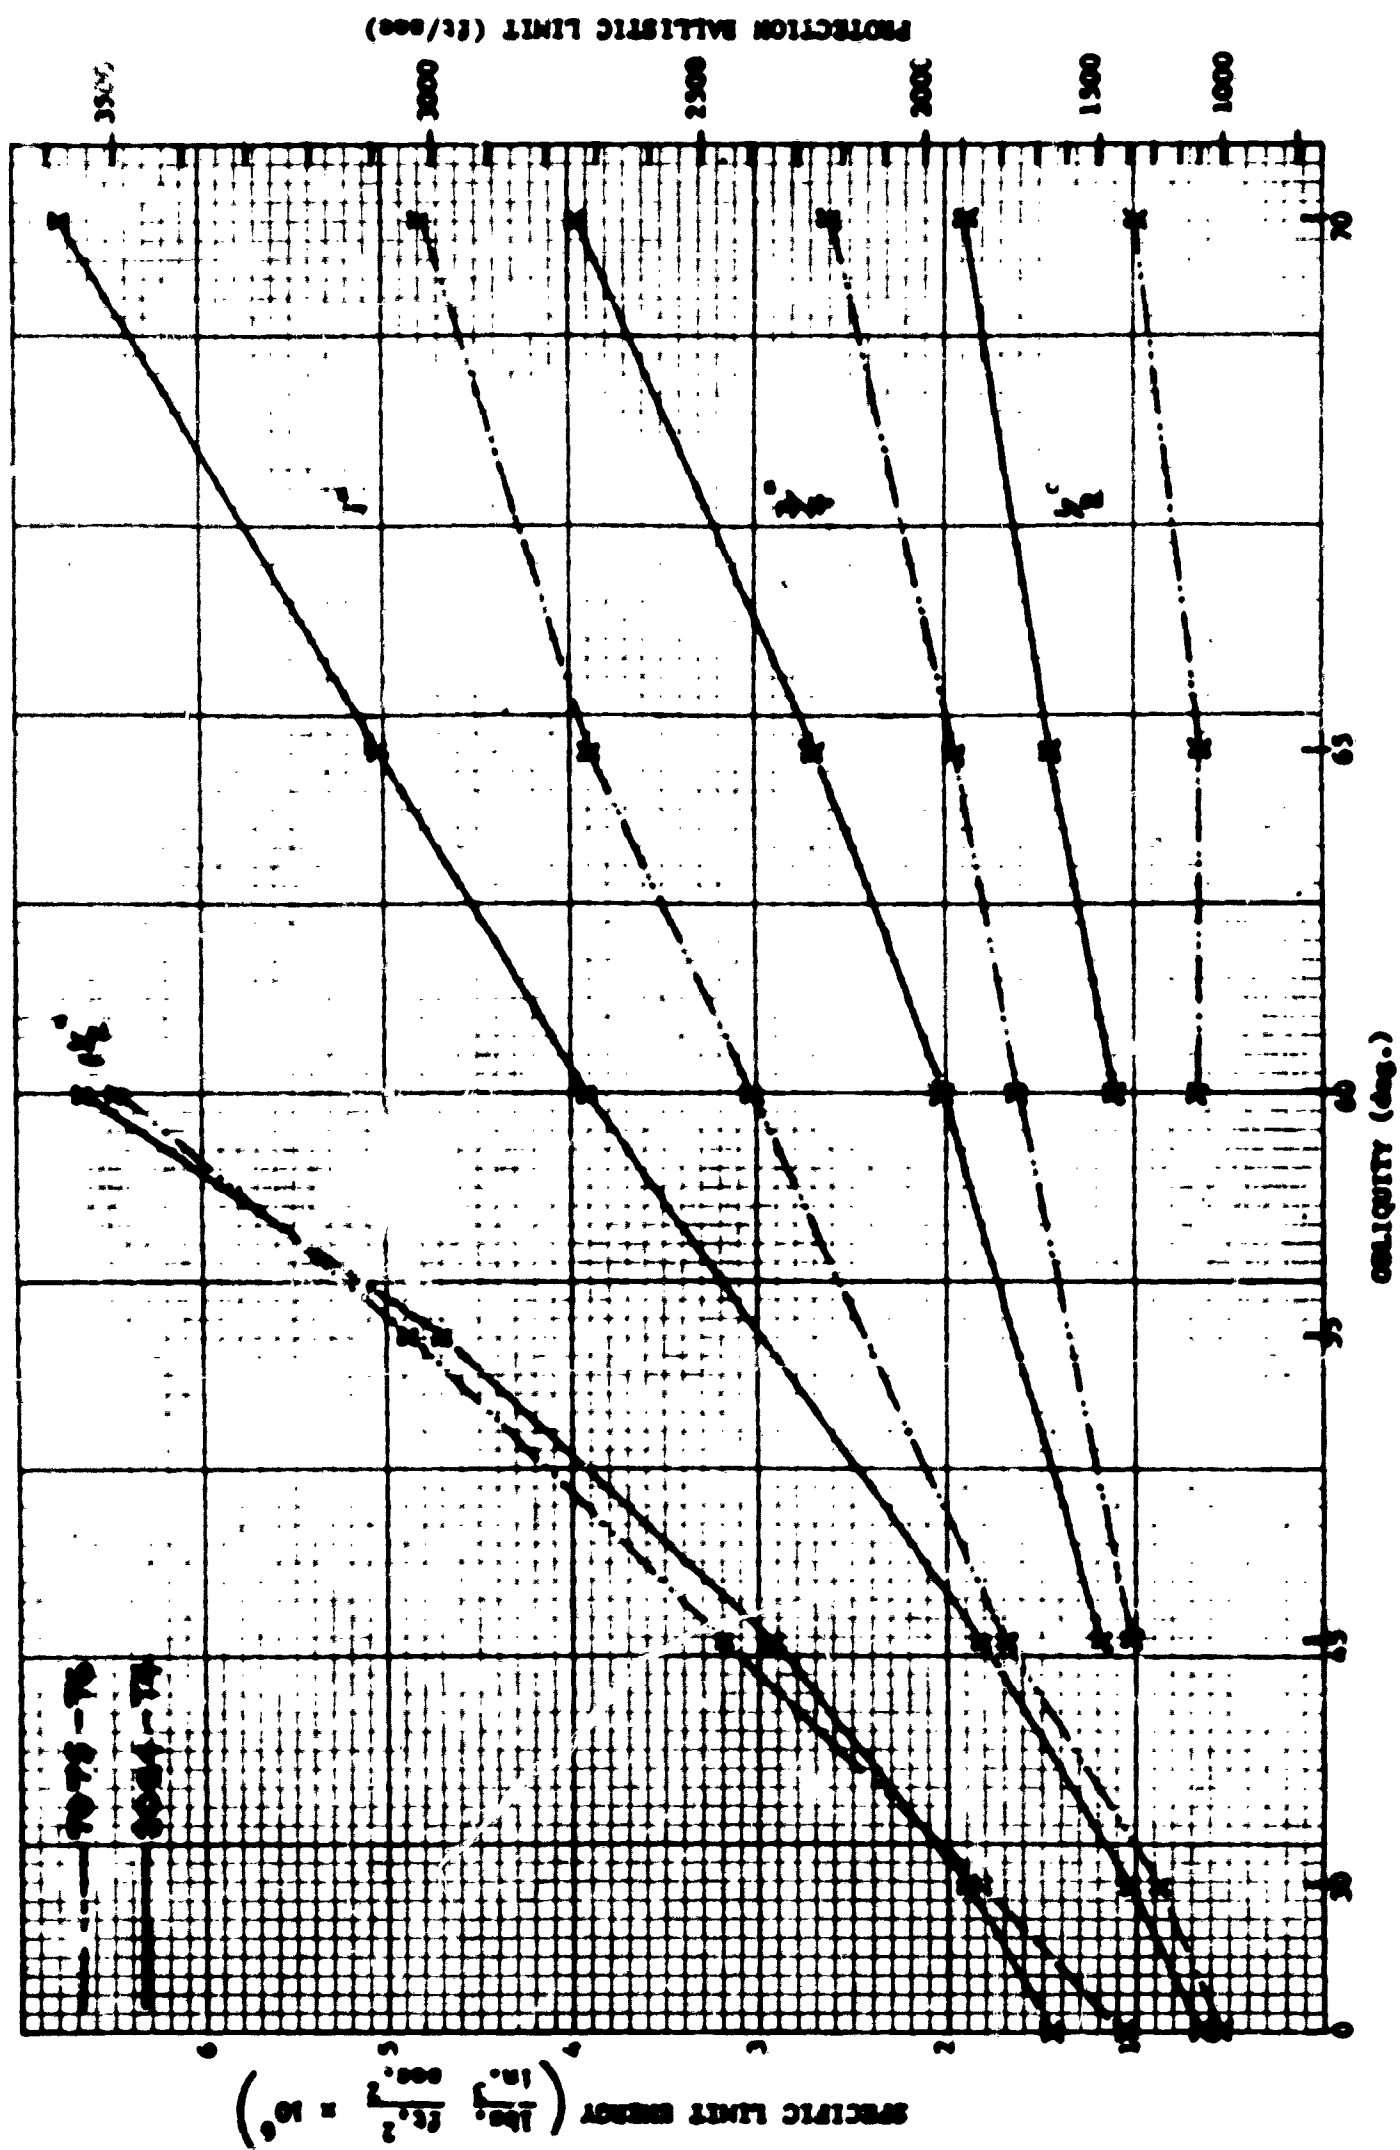

CONFIDENTIAL

Figure 2. Ballistic resistance of 2024-T4 and 7075-T6 aluminum alloy plate vs 20 mm AP T53 projectiles

CONFIDENTIAL

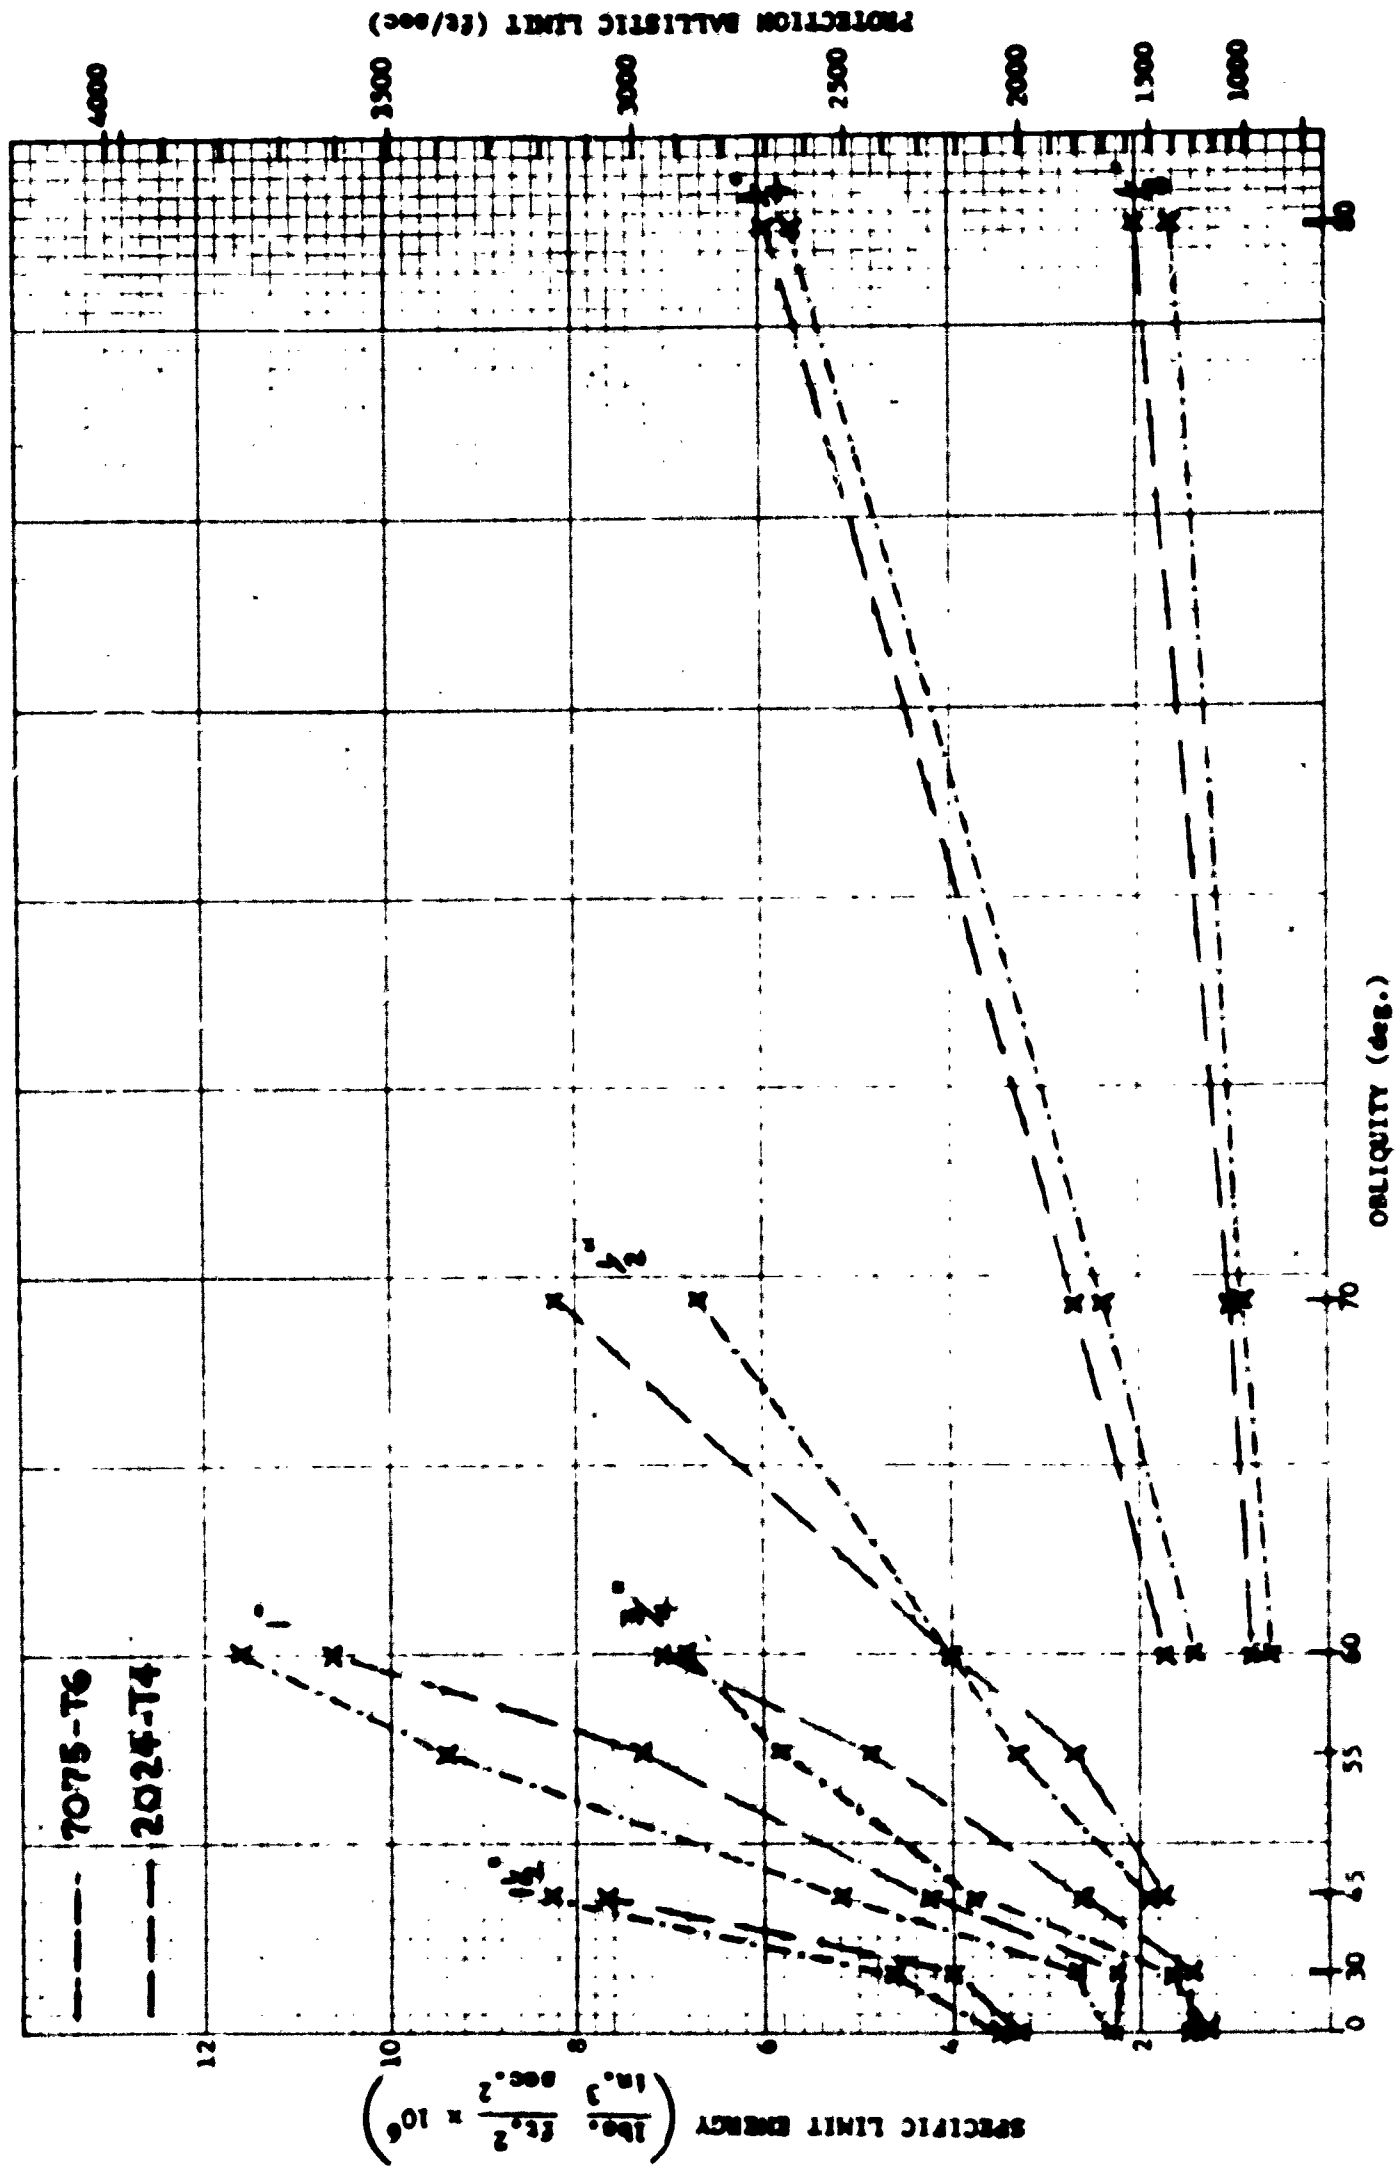

CONFIDENTIAL

Figure 3. Ballistic resistance of 2024-T4 and 7075-T6 aluminum alloy plates vs caliber .50 AP M2 projectile

CONFIDENTIAL


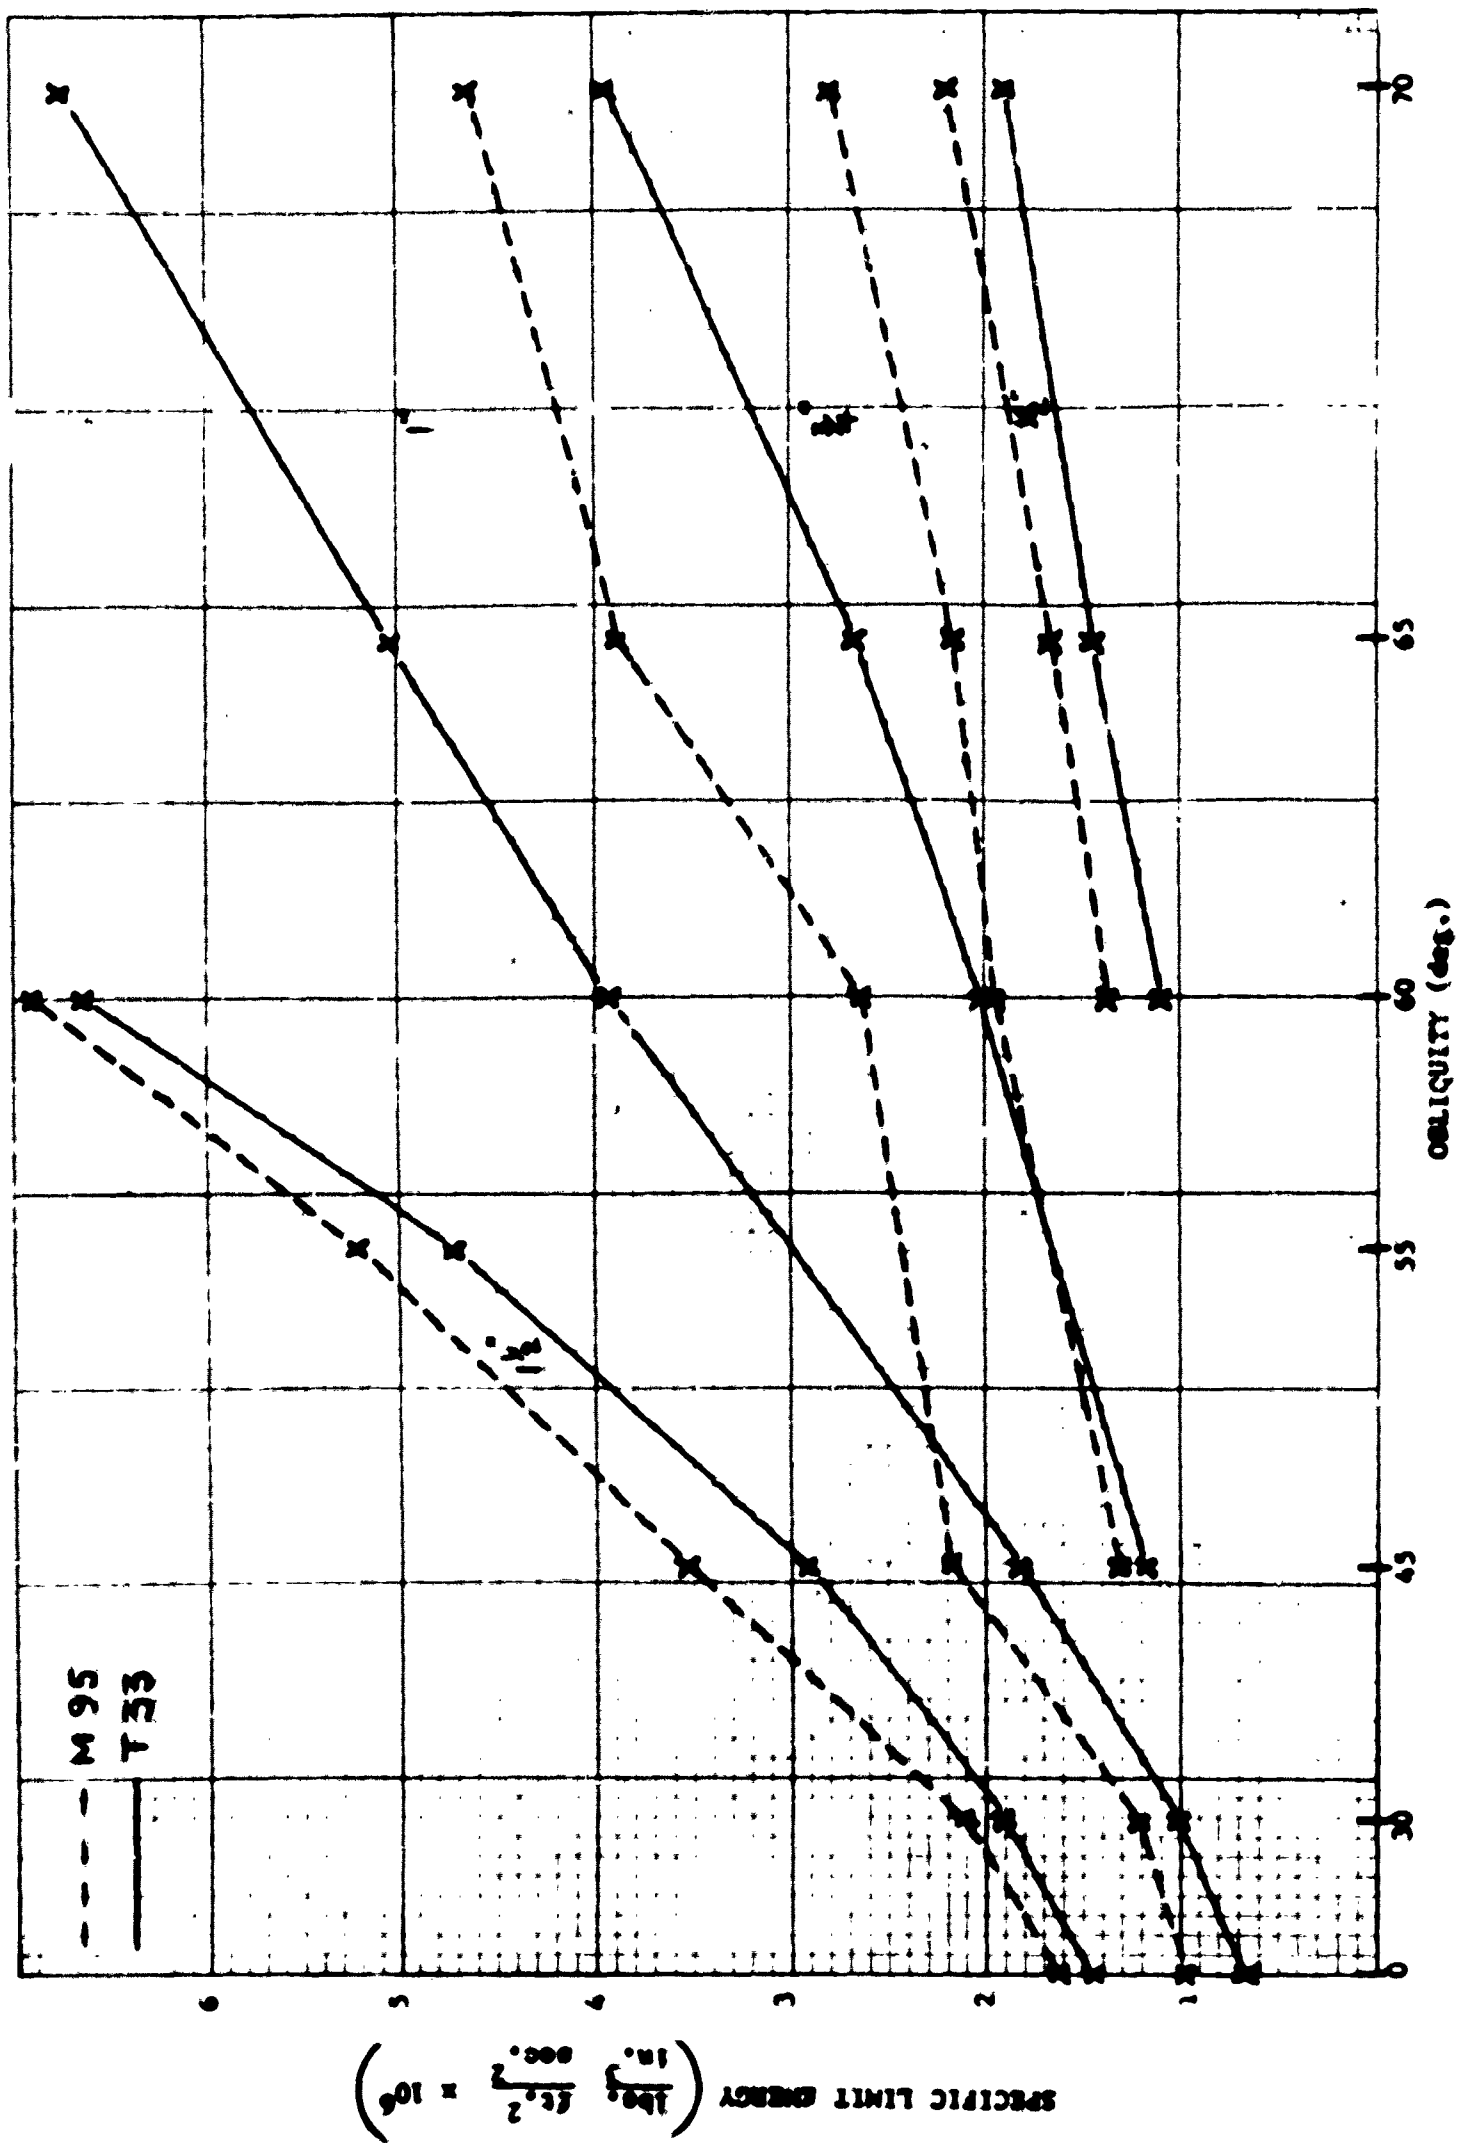


Figure 4. Ballistic performance of 20 mm AP M95 and AP T33 projectiles vs 2024-T4 aluminum alloy plate

CONFIDENTIAL

CONFIDENTIAL

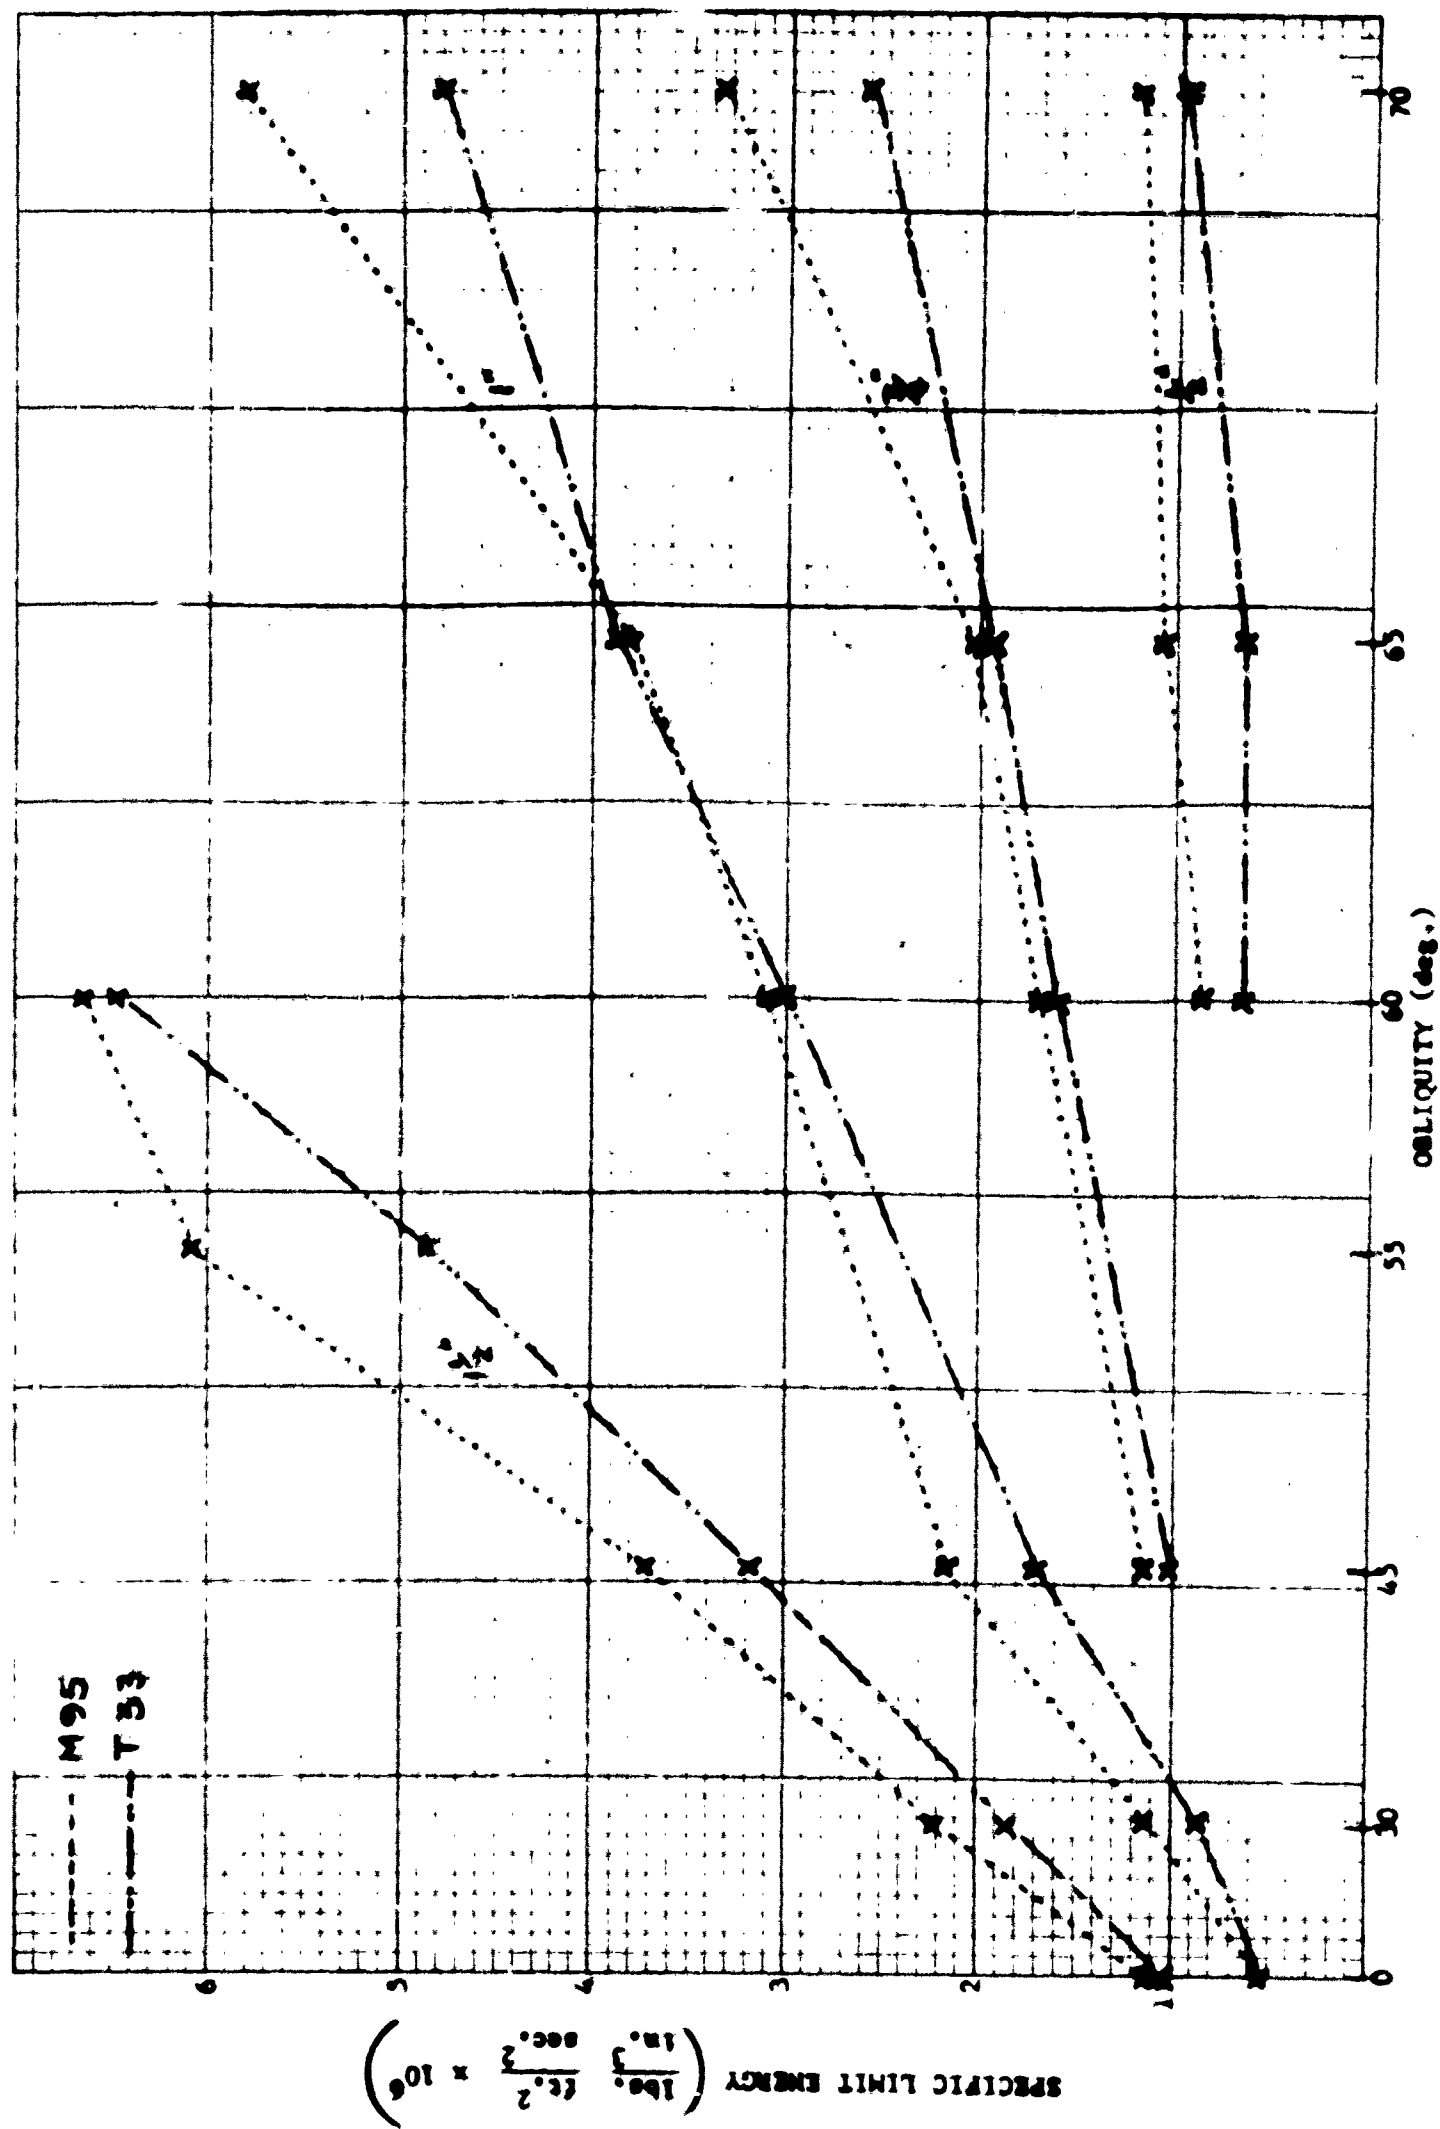


CONFIDENTIAL


Figure 5. Ballistic performance of 20 mm AP M95 and AP T33 projectiles vs 7075-T6 aluminum alloy plate

**CONFIDENTIAL**

Neg. #34213  
R-1395

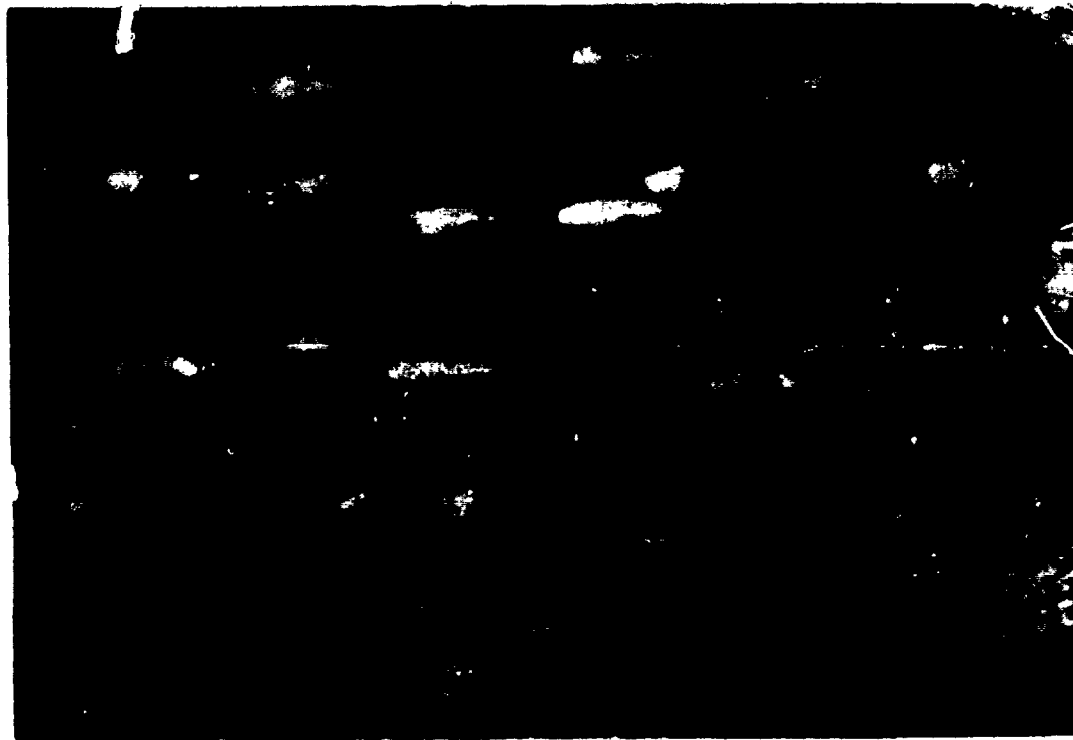

A

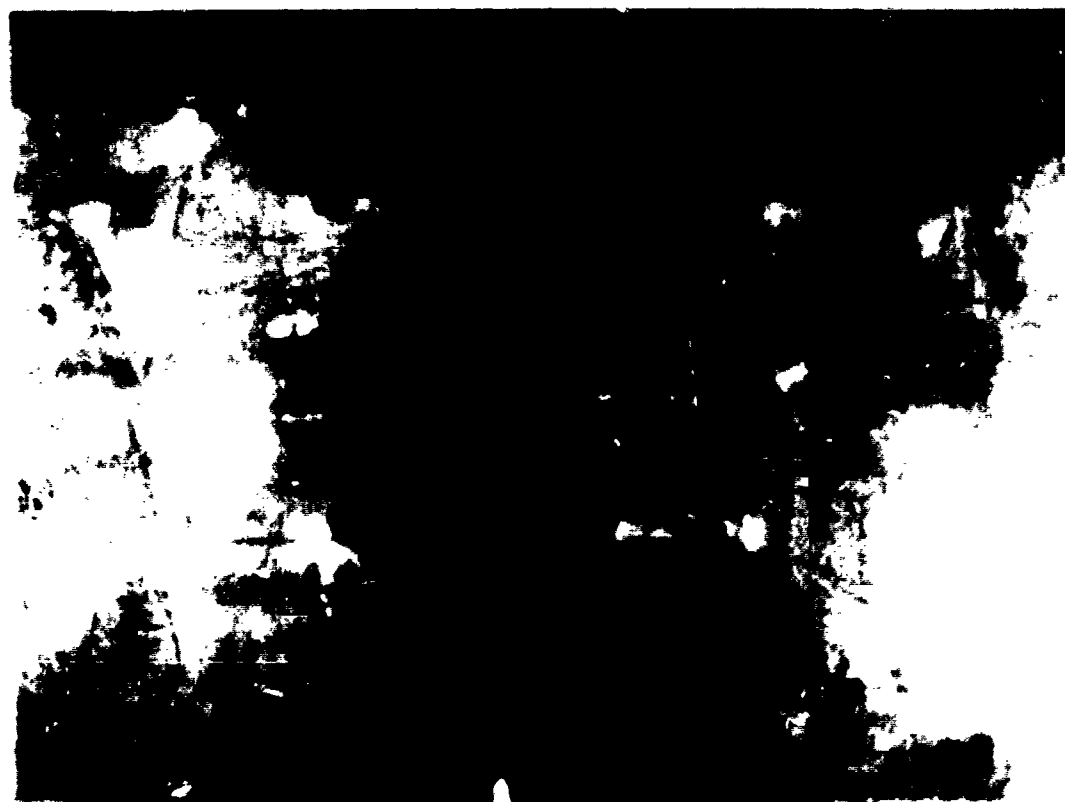

B

**Figure 6. 20 mm projectile impacts on 1/2 inch 2024-T4 aluminum alloy plate**

**A - Front surface**


**B - Rear surface**

(Rounds 1 to 4 (AP T33) and rounds 5 to 11 (AP M95) at 60° obliquity;  
rounds 12 to 15 (AP T33) and rounds 16 to 19 (AP M95) at 70° obliquity)

**CONFIDENTIAL**

**CONFIDENTIAL**

Neg. #34214  
R-1395

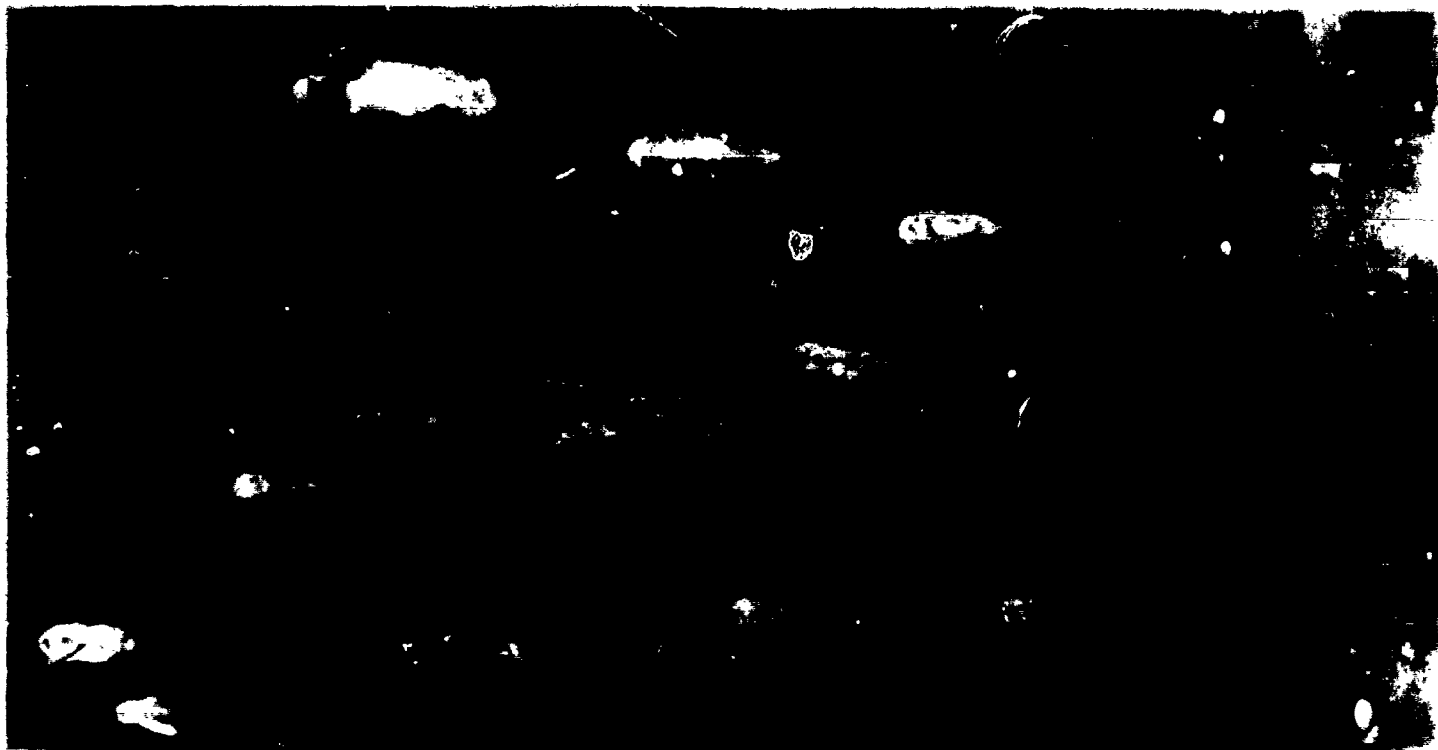

A



B

Figure 7. 20 mm projectile impacts on 1/2 inch 7075-T6 aluminum alloy plate

A - Front surface


B - Rear surface

(Rounds 1 to 6 (AP T33) and rounds 7 to 12 (AP M95) at 60° obliquity)



**CONFIDENTIAL**

Neg. #34215  
R-1395

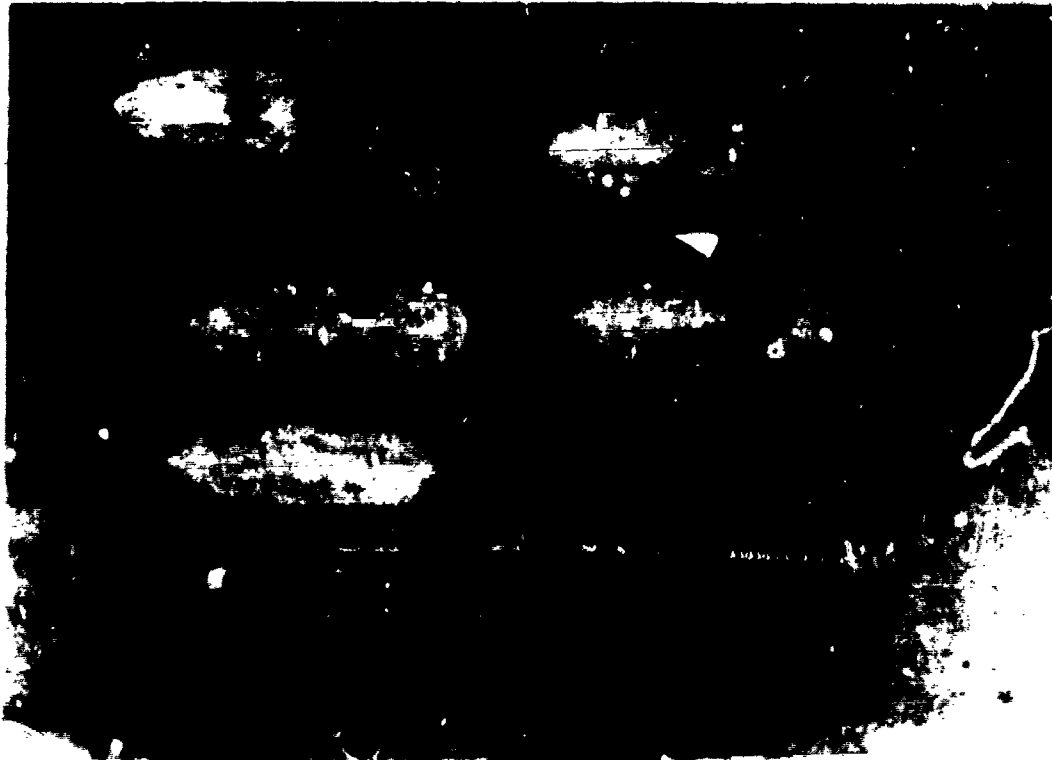

**Figure 8. 20 mm projectile impacts on 1 1/2 inch 2024-T4 aluminum alloy plate**

**A - Front surface**

**B - Rear surface**

**(Rounds 1 to 5 (AP T33) at 60° obliquity; rounds 6, 7, 8, 9, and 18 (AP T33)  
and 10 to 17 (AP M95) at 0° obliquity)**


**CONFIDENTIAL**

**CONFIDENTIAL**

Neg. #34216  
R-1395



A

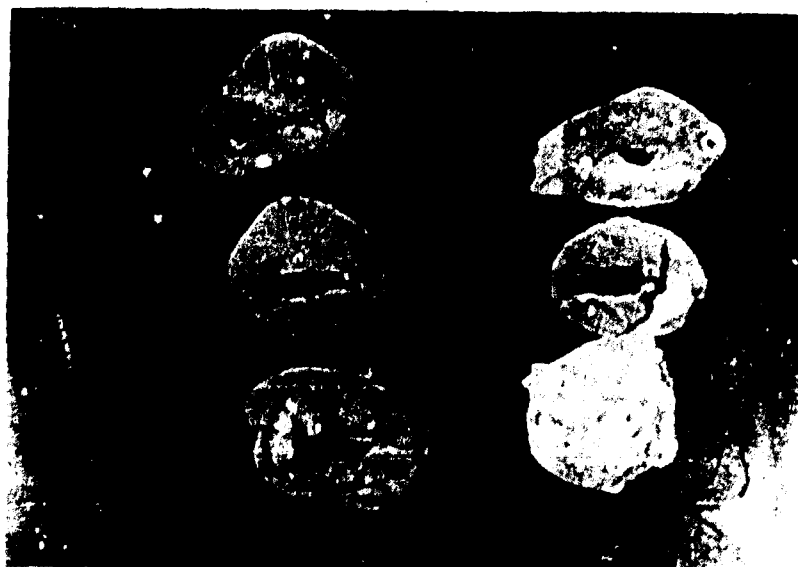


B

Figure 9. 20 mm AP T33 projectile impacts on 1 1/2 inch 7075-T6 aluminum alloy plate at 60° obliquity

A - Front surface    B - Rear surface

**CONFIDENTIAL**

**CONFIDENTIAL**

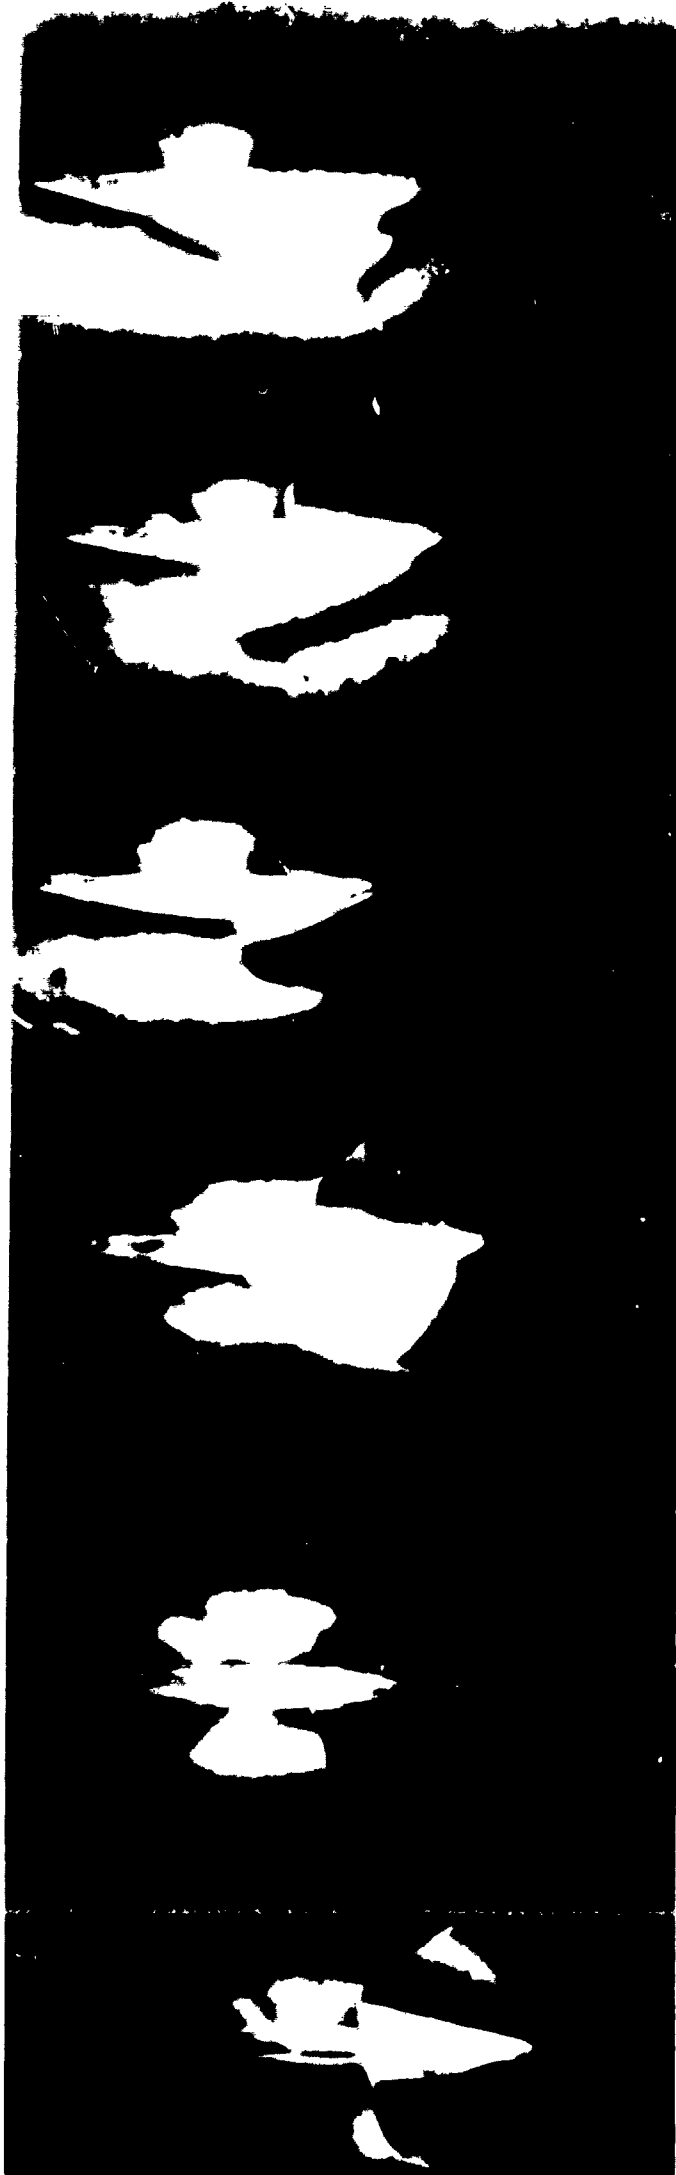

A




**Figure 10. Caliber .50 AP M2 projectile impacts on 1/4 inch 2024-T4 aluminum alloy plate  
at 80° obliquity**


**A - Front surface**

**B - Rear surface**

CONFIDENTIAL

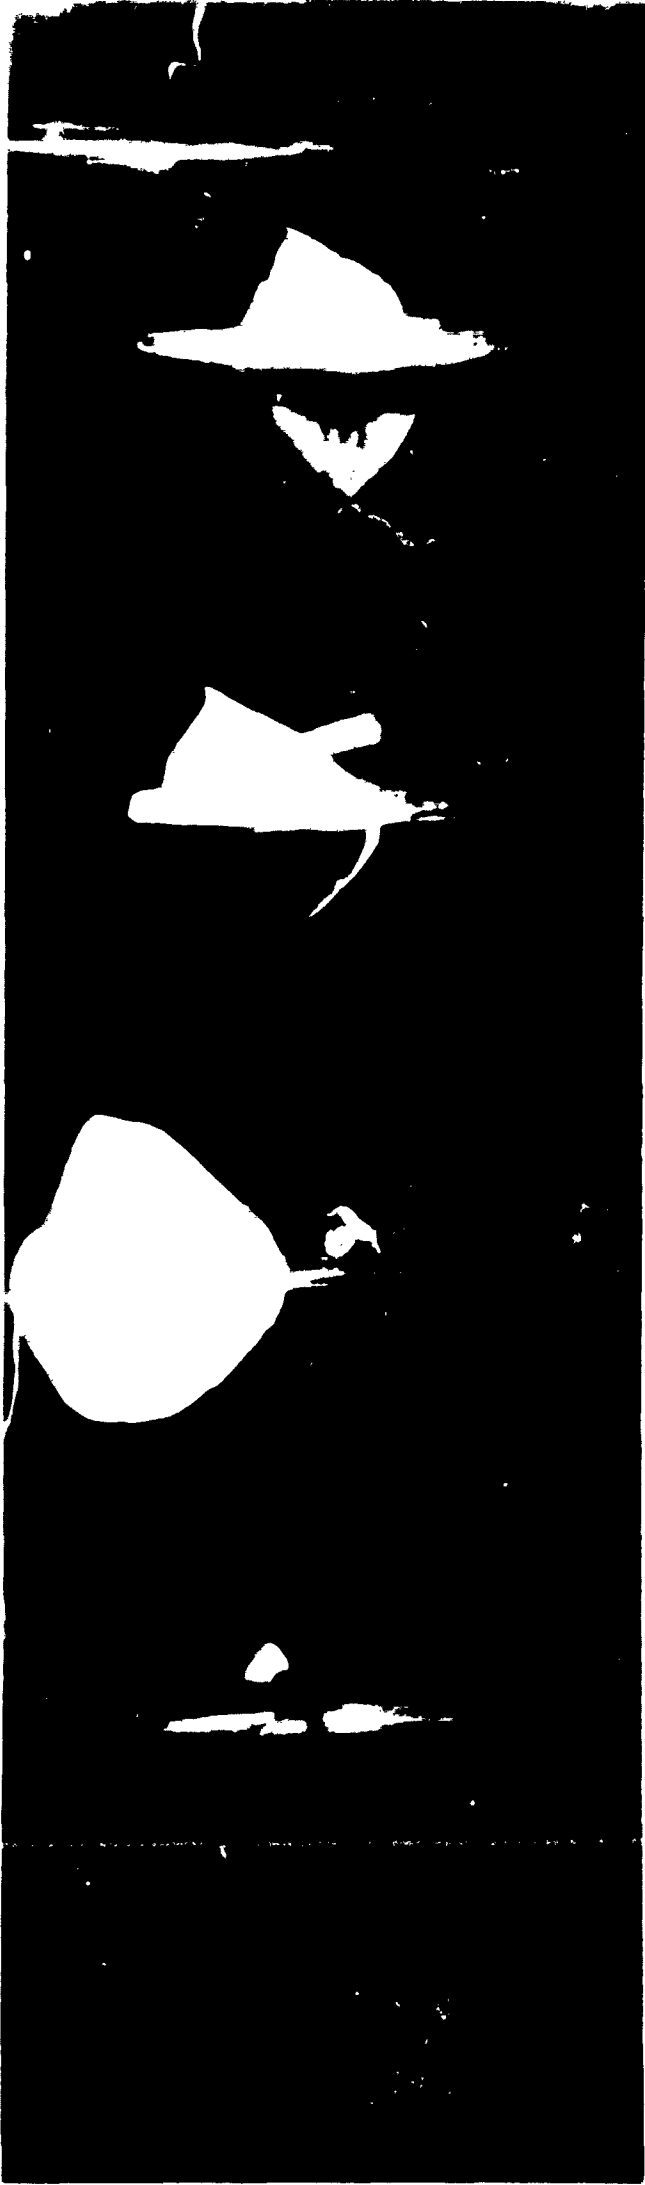

A

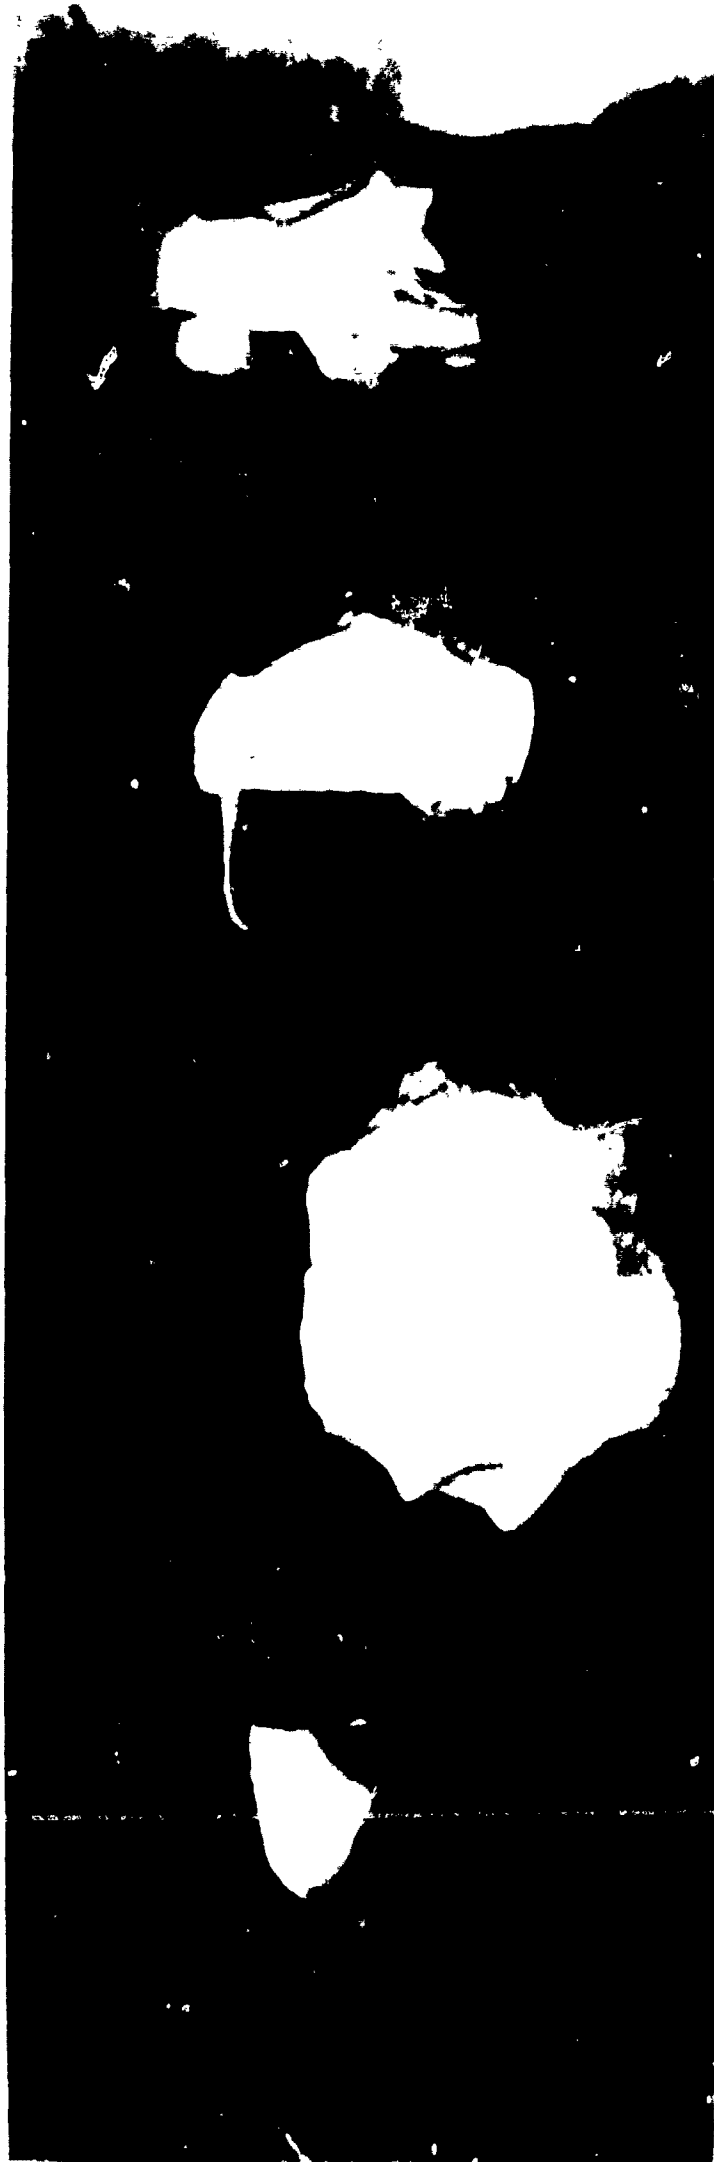

B

Figure 11. Caliber .50 AM M2 projectile impacts on 1/4 inch 7075-T6 aluminum alloy plate  
at 80° obliquity

A - Front surface

B - Rear surface

# CONFIDENTIAL

## DISTRIBUTION LIST

- |  |  |
|--|--|
| 1 - Chief of Ordnance<br>Department Army<br>Washington 25, D. C.<br>Attn: ORDTB                                  | 1 - Commanding General<br>Aberdeen Proving Ground<br>Maryland<br>Attn: Ball Res Lab                              |
| 1 - Director<br>Ordnance Materials Research Office<br>Watertown Arsenal<br>Watertown 72, Mass.<br>Attn: PS&C Div | 1 - Attn: D&PS, Armor Branch   |
| 1 - Commanding Officer<br>Lake City Arsenal<br>Independence, Missouri  | 1 - Attn: Tech Info Br, Bldg 313   |
| 1 - Commanding General<br>Picatinny Arsenal<br>Dover, New Jersey<br>Attn: Tech Group                             | 1 - Commanding General<br>Ordnance Ammunition Command<br>U. S. Army<br>Joliet, Illinois<br>Attn: Materials Eng   |
| 1 - Commanding Officer<br>Redstone Arsenal<br>Huntsville, Alabama<br>Attn: R & D Group                           | 1 - Commander<br>Ordnance-Tank Automotive Command<br>Detroit Arsenal<br>Center Line, Michigan<br>Attn: R & D Div |
| 1 - Commanding Officer<br>Rock Island Arsenal<br>Rock Island, Illinois<br>Attn: Laboratory                       | 1 - Attn: ORDNC II.60  |
| 1 - Commanding Officer<br>Springfield Armory<br>Springfield 1, Mass.<br>Attn: Eng Dept                           | 2 - Commander<br>Ordnance Weapons Command<br>Rock Island Arsenal<br>Rock Island, Illinois<br>Attn: ORDOW-TX      |
| 1 - Commanding Officer<br>Watertown Arsenal<br>Watertown 72, Mass.<br>Attn: WAL                                  | 1 - Chief<br>Bureau of Ordnance<br>Navy Department<br>Washington 25, D. C.                                       |
| 1 - Commander<br>Army Ballistics Missile Agency<br>Redstone Arsenal<br>Huntsville, Alabama                       | 1 - Chief<br>Bureau of Aeronautics<br>Navy Department<br>Washington 25, D. C.                                    |
|  | 1 - Chief<br>Bureau of Ships<br>Navy Department<br>Washington 25, D. C.<br>Attn: Code 343                        |

# CONFIDENTIAL

- 1 - Director  
Naval Research Laboratories  
Washington 25, D. C.
- 1 - Commander  
Naval Ordnance Laboratories  
Silver Spring 19 Maryland
- 1 - Commandant  
U. S. Naval Proving Ground  
Dahlgren, Virginia  
Attn: Terminal Ballistics Lab
- 1 - Commanding General  
Wright Air Development Center  
Wright-Patterson Air Force Base  
Dayton, Ohio  
Attn: Materials Laboratory
- 1 - Headquarters  
Air Research and Development Command  
P. O. Box 1395  
Baltimore 3, Maryland  
Attn: RDTDA
- 1 - Commanding Officer  
Diamond Ordnance Fuze Laboratories  
Washington 25, D. C.  
Attn: Technical Reference Section  
ORDTL Oct 63
- 5 - Armed Services Technical Information Agency  
Document Service Center  
Knott Building  
Dayton 2, Ohio  
Attn: TICSCP-2  
(Code 3)

CONFIDENTIAL